

ADOPTED: 1 December 2015

PUBLISHED: 12 January 2016

doi:10.2903/j.efsa.2016.4333

Safety assessment of the processes 'Sumilon Eco PET SARL' and 'ITD', based on Starlinger IV+[®] technology, used to recycle post-consumer PET into food contact materials

EFSA Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids (CEF)

Abstract

This scientific opinion of the EFSA Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids deals with the safety evaluation of the recycling processes Sumilon Eco PET SARL and ITD (EU register No. RECYC0125 and RECYC0127, respectively) based on the Starlinger IV+[®] technology. The input of the processes is washed and dried poly(ethylene terephthalate) (PET) flakes originating from collected post-consumer PET containers, containing no more than 5% of PET from non-food applications. These flakes are dried and crystallised in a reactor, then extruded into pellets which are further crystallised in a second reactor. Crystallised pellets are then pre-heated in a third reactor and fed to the solid state polycondensation (SSP) reactor. Having examined the challenge tests provided, the Panel concluded that the three steps, drying and crystallisation, extrusion and crystallisation and SSP are the critical steps that determine the decontamination efficiency. The operating parameters controlling the performance are temperature, gas flow and residence time for the drying and crystallisation step, and temperature, pressure and residence time for the extrusion and crystallisation step and the SSP step. It was demonstrated that the processes Sumilon Eco PET SARL and ITD are able to ensure that the migration of potential unknown contaminants into food is below a conservatively modelled migration of 0.1 µg/kg food. Therefore, the Panel concluded that the recycled PET obtained from these processes intended to be used up to 100% for the manufacture of bottles (for ITD) or materials and articles (for Sumilon Eco PET SARL) for contact with all types of foodstuffs for long-term storage at room temperature, with or without hotfill, is not considered of safety concern. Trays made of the recycled PET obtained from the process Sumilon Eco PET SARL are not intended to be used, and should not be used in microwave and conventional ovens.

© European Food Safety Authority, 2016

Keywords: Starlinger IV+, Sumilon Eco PET SARL, ITD, food contact materials, plastic, poly(ethylene terephthalate) (PET), recycling process, safety assessment

Requestor: Bundesamt für Verbraucherschutz und Lebensmittelsicherheit, Germany

Question number: EFSA-Q-2015-00114 and EFSA-Q-2015-00245

Correspondence: fip@efsa.europa.eu

Panel members: Claudia Bolognesi, Laurence Castle, Jean-Pierre Cravedi, Karl-Heinz Engel, Paul Fowler, Roland Franz, Konrad Grob, Rainer Gürtler, Trine Husøy, Sirpa Kärenlampi, Wim Mennes, Maria Rosaria Milana, André Penninks, Vittorio Silano, Andrew Smith, Maria de Fátima Tavares Poças, Christina Tlustos, Detlef Wölfe, Holger Zorn and Corina-Aurelia Zugravu.

Competing interests: In line with EFSA's policy on declarations of interest, Roland Franz did not participate in the development and adoption of this scientific output.

Acknowledgements: The Panel wishes to thank the members of the Working Group on Recycling plastics: Laurence Castle, Vincent Dudler, Nathalie Gontard, Eugenia Lampi, Maria Rosaria Milana, Cristina Nerin, Constantine Pappaspyrides and Maria de Fátima Tavares Poças for the preparatory work on this scientific output, and EFSA staff member: Cristina Croera for the support provided to this scientific output.

Suggested citation: EFSA CEF Panel (EFSA Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids), 2015. Scientific opinion on the safety assessment of the processes 'Sumilon Eco PET SARM' and 'ITD', based on Starlinger IV+[®] technology, used to recycle post-consumer PET into food contact materials. EFSA Journal 2016;14(1):4333, 14 pp. doi:10.2903/j.efsa.2016.4333

ISSN: 1831-4732

© European Food Safety Authority, 2016



The EFSA Journal is a publication of the European Food Safety Authority, an agency of the European Union.



Table of contents

Abstract.....	1
1. Introduction.....	4
1.1. Background and Terms of Reference as provided by the requestor	4
2. Data and Methodologies	4
2.1. Data.....	4
2.2. Methodologies	5
2.2.1. The principles of the evaluation scheme	5
3. Assessment	5
3.1. Introduction.....	5
3.2. General information	5
3.3. Description of the process	5
3.3.1. General description	5
3.3.2. Characterisation of the input.....	6
3.4. Starlinger IV+ [®] technology.....	6
3.4.1. Description of the main steps.....	6
3.4.2. Decontamination efficiency of the recycling process	7
3.5. Discussion	8
4. Conclusions	9
5. Recommendations.....	10
Documentation provided to EFSA	11
References.....	11
Appendix A – Technical data of the washed flakes as provided by the applicant of process Sumilon Eco PET SARL	12
Appendix B – Technical data of the washed flakes as provided by the applicant of process ITD ...	12
Appendix C – Relationship between the key parameters for the evaluation scheme (EFSA CEF Panel, 2011)	13
Abbreviations	14

1. Introduction

1.1. Background and Terms of Reference as provided by the requestor

Recycled plastic materials and articles shall only be placed on the market for food contact if they contain recycled plastic obtained from an authorised recycling process. Before a recycling process is authorised, EFSA's opinion on its safety is required. This procedure has been established in Article 5 of the Regulation (EC) No 282/2008¹ of the Commission of 27 March 2008 on recycled plastic materials intended to come into contact with foods and Articles 8 and 9 of the Regulation (EC) No 1935/2004² of the European Parliament and of the Council of 27 October 2004 on materials and articles intended to come into contact with food.

According to this procedure, the industry submits applications to the Member States competent Authorities which transmit the applications to EFSA for evaluation.

In this case, EFSA received, from the Bundesamt für Verbraucherschutz und Lebensmittelsicherheit, Germany, two applications for evaluation of the recycling processes Sumilon Eco PET SARL, EU register No RECYC0125 and ITD, EU register No RECYC0127.

EFSA is required by Article 5 of Regulation (EC) No 282/2008 of the Commission of 27 March 2008 on recycled plastic materials intended to come into contact with foods to carry out risk assessments on the risks originating from the migration of substances from recycled food contact plastic materials and articles into food and deliver a scientific opinion on the recycling processes examined.

According to Article 4 of Regulation (EC) No 282/2008, EFSA will evaluate whether it has been demonstrated in a challenge test, or by other appropriate scientific evidence, that the recycling processes Sumilon Eco PET SARL and ITD are able to reduce any contamination of the plastic input to a concentration that does not pose a risk to human health. The PET materials and articles used as input of the process as well as the conditions of use of the recycled PET make part of this evaluation.

2. Data and Methodologies

2.1. Data

Each application is supported by a technical dossier submitted by industry following the EFSA guidelines for the submission of an application for the safety evaluation of a recycling process to produce recycled plastics intended to be used for the manufacture of materials and articles in contact with food, prior to its authorisation (EFSA, 2008). Applications shall be submitted in accordance with Article 5 of the Regulation (EC) No 282/2008.

The following information on the recycling process was provided by the applicant:

- General information:
 - general description
 - existing authorisations
- Specific information:
 - recycling process
 - characterisation of the input
 - determination of the decontamination efficiency of the recycling process
 - characterisation of the recycled plastic
 - intended application in contact with food

¹ Regulation (EC) No 282/2008 of the European parliament and of the council of 27 March 2008 on recycled plastic materials and articles intended to come into contact with foods and amending Regulation (EC) No 2023/2006. OJ L 86, 28.3.2008, p. 9-18.

² Regulation (EC) No 1935/2004 of the European Parliament and of the Council of 27 October 2004 on materials and articles intended to come into contact with food and repealing Directives 80/590/EEC and 89/109/EEC. OJ L 338, 13.11.2004, p. 4-17.

- compliance with the relevant provisions on food contact materials and articles
- process analysis and evaluation
- operating parameters

2.2. Methodologies

2.2.1. The principles of the evaluation scheme

The risks associated with the use of recycled plastic materials and articles in contact with food come from the possible migration of chemicals into the food in amounts that would endanger human health. The quality of the input, the efficiency of the recycling process to remove contaminants, as well as the intended use of the recycled plastic, are crucial points for the risk assessment (see guidelines on recycling plastics: EFSA, 2008).

The criteria for the safety evaluation of a mechanical recycling process to produce recycled poly(ethylene terephthalate) (PET) intended to be used for the manufacture of materials and articles in contact with food are described in the scientific opinion developed by the EFSA Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids (EFSA CEF Panel, 2011). The principle of the evaluation is to apply the decontamination efficiency of a recycling technology or process, obtained from a challenge test with surrogate contaminants, to a reference contamination level for post-consumer PET, conservatively set at 3 mg/kg PET for contaminants resulting from possible misuse. The resulting residual concentration of each surrogate contaminant in recycled PET (*C_{res}*) is compared with a modelled concentration of the surrogate contaminants in PET (*C_{mod}*). This *C_{mod}* is calculated using generally recognised conservative migration models so that the related migration does not give rise to a dietary exposure exceeding 0.0025 µg/kg body weight (bw) per day (i.e. the human exposure threshold value for chemicals with structural alerts for genotoxicity), below which the risk to human health would be negligible. If the *C_{res}* is not higher than the *C_{mod}*, the recycled PET manufactured by such recycling process is not considered of safety concern for the defined conditions of use (EFSA CEF Panel, 2011).

3. Assessment

3.1. Introduction

The European Food Safety Authority was asked by the Bundesamt für Verbraucherschutz und Lebensmittelsicherheit, Germany, to evaluate the safety of the recycling processes Sumilon Eco PET SARL, European Union (EU) register No RECYC0125 and ITD, EU register No RECYC0127. The requests have been registered in EFSA's register of received questions under the number EFSA-Q-2015-00114 and EFSA-Q-2015-00245, respectively. The dossiers were submitted on behalf of Sumilon Eco PET SARL Eco PET SARL, Morocco, and of ITD Ltd, Bulgaria, respectively.

3.2. General information

According to the applicants, the recycling processes Sumilon Eco PET SARL and ITD are intended to recycle food grade PET containers to produce recycled PET pellets using the Starlinger IV+[®] technology. The recycled pellets are intended to be used up to 100% for the manufacture of recycled bottles (for process ITD) and materials and articles (for process Sumilon Eco PET SARL). These bottles and final materials and articles are intended to be used in direct contact with all kinds of foodstuffs for long-term storage at room temperature, with or without hotfill.

3.3. Description of the process

3.3.1. General description

The recycling processes Sumilon Eco PET SARL and ITD produce recycled PET pellets from PET containers, coming from post-consumer collection systems (kerbside and deposit systems). The recycling processes comprise the four steps below. The first step is performed in house by the applicant of process Sumilon Eco PET SARL, and by third parties in the case of process ITD.

Input

- In step 1, post-consumer PET bottles/containers are sorted and processed into hot caustic washed and dried flakes, which are used as input to the processes.

Decontamination and production of recycled PET material

- In step 2, the flakes are dried and crystallised in a reactor under air using high temperature, at atmospheric pressure.
- In step 3, the flakes are extruded into pellets under vacuum at high temperature and then re-crystallised.
- In step 4, the crystallised pellets are pre-heated before being handled in a continuous running solid state polycondensation (SSP) reactor at high temperature and under vacuum.

The operating conditions of the processes have been provided to EFSA.

Recycled PET pellets, the final product of the process, are checked against technical requirements on intrinsic viscosity, colour, black spots, etc. Recycled PET pellets are intended to be converted by other companies into recycled articles used for hotfill and/or long-term storage at room temperature, such as bottles for mineral, still, and carbonated water, soft drinks, juices and beer for both the processes, also for sauces and condiments for process Sumilon Eco PET SARL. The recycled pellets from the process Sumilon Eco PET SARL may also be used for sheets which are thermoformed to make food trays. Trays made of this recycled PET are not intended to be used in microwave and conventional ovens. Recycled pellets manufactured in Morocco by Sumilon Eco PET SARL are intended to be placed on the European market.

3.3.2. Characterisation of the input

According to the applicants, the input material for the recycling processes Sumilon Eco PET SARL and ITD is hot caustic washed and dried flakes obtained from PET containers, mainly bottles, previously used for food packaging, from post-consumer collection systems (kerbside and deposit systems). However, a small fraction may originate from non-food applications, such as soap bottles, mouthwash bottles, kitchen hygiene bottles, etc. According to the applicants, the amount of this non-food container fraction depends on the re-collection system. On the basis of market share data, the applicants estimated that this fraction is below 5%.

According to the applicants, the post-consumer PET containers have been manufactured in accordance with Community legislation on plastic food contact materials and articles.

Technical data for the washed and dried flakes are provided, such as information on residual content of poly(vinyl chloride) (PVC), glue, polyolefins, metals, and physical properties (see Appendix A and B).

3.4. Starlinger IV+[®] technology

3.4.1. Description of the main steps

To decontaminate post-consumer PET, the recycling processes Sumilon Eco PET SARL and ITD use the Starlinger IV+[®] technology as described below and for which the general scheme provided by the applicants is reported in Figure 1. Figure 1 starts at Step 2. Step 1 is the washing step performed by the flakes suppliers for process ITD and in house for process Sumilon Eco PET SARL.

- Drying and crystallisation (step 2): In this step the flakes are dried and crystallised at high temperature in a reactor under air and at atmospheric pressure, in a continuous process.
- Extrusion and crystallisation (step 3): The flakes from the previous step are fed into an extruder under high temperature and vacuum for a predefined residence time. Further decontamination occurs in this step. The extruded pellets are then crystallised at high temperature in a further reactor under atmospheric pressure.

- SSP (step 4): The crystallised pellets are continuously pre-heated in a reactor before being introduced into the SSP reactor running under vacuum at a predefined high temperature and for a predefined residence time.

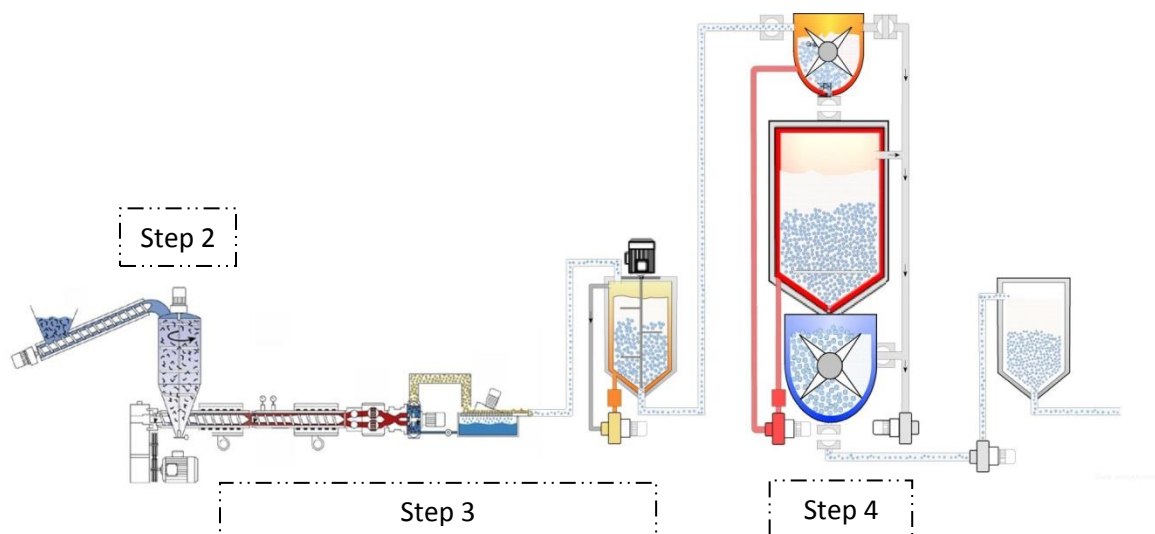


Figure 1: General scheme of the Starlinger IV+[®] technology

The processes are operated under defined operating parameters of temperature, pressure, gas flow and residence time.

3.4.2. Decontamination efficiency of the recycling process

To demonstrate the decontamination efficiency of the recycling processes Sumilon Eco PET SARR and ITD, a challenge test on the Starlinger IV+[®] technology was submitted to EFSA.

PET flakes were contaminated with selected chemicals, toluene, chloroform, phenylcyclohexane, benzophenone and lindane, used as surrogate contaminants. The surrogates were chosen in agreement with EFSA guidelines and in accordance with the recommendations of the US Food and Drug Administration. The surrogates include different molecular weights and polarities to cover possible chemical classes of contaminants of concern and were demonstrated to be suitable to monitor the behaviour of PET during recycling (EFSA, 2008).

For the preparation of the contaminated PET flakes, conventionally recycled³ green PET flakes were soaked in a heptane/isopropanol solution containing the surrogates and stored for 14 days at 40°C. The surrogates solution was decanted and PET flakes were rinsed with water and then air dried. The concentration of surrogates in this material was determined.

The Starlinger IV+[®] technology was challenged in Starlinger facilities in a pilot plant scale and using only contaminated flakes. The contaminated flakes were introduced directly in the drier (step 2) then sampled after each step (2–4) of the process. The samples (flakes then pellets) were analysed for their residual concentrations of the applied surrogates. Instead of being processed continuously, the SSP reaction was run in batch mode. In both batch and continuous modes of operation the surrogates diffuse through the pellets to the surface and they are constantly eliminated by the vacuum applied. Therefore, continuous working processes will result in the same cleaning efficiencies as batch processes, as long as the same temperature, pressure conditions and residence time are applied.

The decontamination efficiency of the process was calculated taking into account the amount of the surrogates detected in contaminated flakes before drying and crystallisation (before step 2) and after

³ Conventional recycling includes commonly sorting, grinding, washing and drying steps and produces washed and dried flakes.

SSP (step 4). When not detected, the limit of detection was considered for the calculation of the decontamination efficiency. The results are summarised below in Table 1.

Table 1: Efficiency of the decontamination of the Starlinger IV+[®] technology in the challenge test.

Surrogates	Concentration of surrogates before step 2 (mg/kg PET)	Concentration of surrogates after step 4 (mg/kg PET)	Decontamination efficiency (%)
Toluene	563	< 0.8 ^(a)	> 99.9
Chloroform	1 900	< 0.5 ^(a)	> 99.9
Phenylcyclohexane	538	< 0.3 ^(a)	> 99.9
Benzophenone	694	10.8	98.4
Lindane	373	33.9	90.9

(a): Not detected at the limits of detection given.

As shown above, the decontamination efficiency ranged from 90.9% for lindane to more than 99.9% for toluene, chloroform and phenylcyclohexane.

3.5. Discussion

Considering the high temperatures used during the process, the possibility of contamination by microorganisms can be discounted. Therefore, this evaluation focuses on the chemical safety of the final product.

Technical data, such as information on residual content of PVC, glue, polyolefins, metals and physical properties, are provided for the input materials (washed and dried flakes (step 1)) for the submitted recycling processes. The input materials are produced from PET containers previously used for food packaging collected through post-consumer collection systems. However, a small fraction may originate from non-food applications, such as soap bottles, mouthwash bottles, kitchen hygiene bottles, etc. According to the applicant, the amount of this non-food container fraction depends on the re-collection system and, on the basis of market share data, it is below 5%, as recommended by the EFSA CEF Panel in its 'Scientific opinion on the criteria to be used for safety evaluation of a mechanical recycling process to produce recycled PET intended to be used for manufacture of materials and articles in contact with food' (EFSA CEF Panel, 2011). According to the applicants, all usual non-food use PET containers are manufactured from food grade PET material and hence should be in compliance with Regulation (EU) No 10/2011.

The processes are well described. The production of washed and dried flakes from collected containers (step 1) is conducted by the applicant (for process Sumilon Eco PET SARL) or by third parties (for process ITD) and, according to both applicants, this step is under control. The following steps are those of the Starlinger IV+[®] technology used to recycle the PET flakes into decontaminated PET pellets: drying and crystallisation (step 2), extrusion and crystallisation (step 3) and SSP (step 4). The operating parameters of temperature, pressure, residence time and gas flow have been provided to EFSA.

A challenge test was conducted at a pilot plant scale on process steps 2 to 4 (drying, extrusion and crystallisation, and SSP reactors) to measure the decontamination efficiency. The operating parameters of these steps in the processes are at least as severe as those operated for the challenge test. The Panel considered that the challenge test was performed correctly according to EFSA guidelines (EFSA, 2008). Although the fourth step is expected to be the most critical step for the decontamination, drying and crystallisation (step 2) and extrusion (step 3) are relevant too. Therefore, the Panel considered that the three steps (drying and crystallisation, extrusion and crystallisation, and SSP) are the critical steps for the decontamination efficiency of the process. Consequently, the temperature, the gas flow and the residence time for the drying and crystallisation (step 2), and the temperature, the pressure and the residence time for extrusion and crystallisation (step 3) and SSP (step 4) should be controlled to guarantee the performance of the decontamination. These parameters have been provided to EFSA.

The decontamination efficiencies obtained for each surrogate contaminant from the challenge test, ranging from 90.9% to above 99.9%, have been used to calculate the residual concentrations of potential unknown contaminants in pellets (*C_{res}*) in accordance with the evaluation procedure

described in the 'Scientific opinion on the criteria to be used for safety evaluation of a mechanical recycling process to produce recycled PET' (EFSA CEF Panel, 2011; Appendix B). By applying the decontamination efficiency percentage to the reference contamination level of 3 mg/kg PET, the *Cres* for the different surrogates is obtained (Table 2).

The CEF Panel noted that the input of the process Sumilon Eco PET SARL originates from Morocco, Africa. The level of contamination determined in the EU survey (EFSA CEF Panel, 2011) is not necessarily representative for input collected outside of the EU. The frequency and the severity of misuse and contamination could be different on another market, but no corresponding data was available. For the purpose of this evaluation the Panel used the reference contamination of 3 mg/kg PET derived from experimental data on severity and frequency of contamination of washed and dried flakes reported in the EU survey.

According to the evaluation principles (EFSA CEF Panel, 2011), the *Cres* value should not be higher than a modelled concentration in PET (*Cmod*) corresponding to a migration, after one year at 25°C, which cannot give rise to a dietary exposure exceeding 0.0025 µg/kg bw/day, the exposure threshold below which the risk to human health would be negligible⁴. Because the recycled PET is intended for general use for the manufacturing of articles containing up to 100% recycled PET, the most conservative default scenario for infants has been applied. Therefore, the migration of 0.1 µg/kg into food has been used to calculate *Cmod* (EFSA CEF Panel, 2011). The results of these calculations are shown in Table 2. The relationship between the key parameters for the evaluation scheme is reported in Appendix C.

Table 2: Decontamination efficiency from challenge test, residual concentration of surrogate contaminants in recycled PET (*Cres*) and calculated concentration of surrogate contaminants in PET (*Cmod*) corresponding to a modelled migration of 0.1 µg/kg food after one year at 25°C.

Surrogates	Decontamination efficiency (%)	<i>Cres</i> (mg/kg PET)	<i>Cmod</i> (mg/kg PET)
Toluene	> 99.9	< 0.003	0.09
Chloroform	> 99.9	< 0.003	0.10
Phenylcyclohexane	> 99.9	< 0.003	0.14
Benzophenone	98.4	0.048	0.16
Lindane	90.9	0.273	0.31

The residual concentrations of all surrogates in PET after decontamination (*Cres*) are lower than the corresponding modelled concentrations in PET (*Cmod*). Therefore, the Panel considered that the recycling processes Sumilon Eco PET SARL and ITD using Starlinger IV+[®] technology are able to ensure that the level of migration of unknown contaminants from the recycled PET into food is below the conservatively modelled migration of 0.1 µg/kg food at which the risk to human health would be negligible.

The above calculations are based on the reference contamination level of 3 mg/kg (EFSA CEF Panel, 2011). Therefore the reference contamination level calculated for the market from which the input originates should be comparable to or below the reference contamination level determined for the EU market.

4. Conclusions

The CEF Panel considered that the processes Sumilon Eco PET SARL and ITD are well characterised and the main steps used to recycle PET flakes into decontaminated PET pellets have been identified. Having examined the challenge test provided, the Panel concluded that the three steps (drying and crystallisation, extrusion and crystallisation, and SSP) are the critical steps for the decontamination efficiency of the process. The operating parameters to control its performance are the temperature,

⁴ 0.0025 µg/kg bw/day is the human exposure threshold value for chemicals with structural alerts raising concern for potential genotoxicity, below which the risk to human health would be negligible (EFSA CEF Panel, 2011).

the gas flow and the residence time for the drying and crystallisation (step 2) and the temperature, the pressure and the residence time for extrusion and crystallisation (step 3) and SSP (step 4).

The Panel considered that the recycling process Sumilon Eco PET SARL is able to reduce any foreseeable accidental contamination of the post-consumer food contact PET to a concentration that does not give rise to concern for a risk to human health if:

- i) the contamination level calculated for the market from which the input material originates, is comparable to or below the reference contamination level determined for the EU market of 3 mg/kg PET; and
- ii) it is operated under conditions that are at least as severe as those obtained from the challenge test used to measure the decontamination efficiency of the process; and
- iii) the input of the process is washed and dried post-consumer PET flakes originating from materials and articles that have been manufactured in accordance with the EU legislation on food contact materials containing no more than 5% of PET from non-food consumer application.

The Panel considered that the recycling process ITD is able to reduce any foreseeable accidental contamination of the post-consumer food contact PET to a concentration that does not give rise to concern for a risk to human health if:

- i) it is operated under conditions that are at least as severe as those obtained from the challenge test used to measure the decontamination efficiency of the process; and
- ii) the input of the process is washed and dried post-consumer PET flakes originating from materials and articles that have been manufactured in accordance with the EU legislation on food contact materials containing no more than 5% of PET from non-food consumer applications.

Therefore, the recycled PET obtained from the processes Sumilon Eco PET SARL and ITD intended to be used up to 100% for the manufacture of bottles (for process ITD) or materials and articles (for process Sumilon Eco PET SARL) for contact with all types of foodstuffs for long-term storage at room temperature, with or without hotfill, is not considered of safety concern. Trays made of this recycled PET obtained from process Sumilon Eco PET SARL are not intended to be used, and should not be used in microwave and conventional ovens.

5. Recommendations

The Panel recommended periodic verification that the input to be recycled originates from materials and articles that have been manufactured in accordance with the EU legislation on food contact materials and that the proportion of PET from non-food consumer applications is no more than 5%. This adheres to good manufacturing practice and the Regulation (EC) No 282/2008, Article 4b. Critical steps in recycling should be monitored and kept under control. In addition, supporting documentation should be available on how it is ensured that the critical steps are operated under conditions at least as severe as those in the challenge test used to measure the decontamination efficiency of the process.

Documentation provided to EFSA

1. Dossier 'Sumilon Eco PET SARL'. May 2015. Submitted on behalf of Sumilon Eco PET SARL Eco PET SARL.
2. Dossier 'ITD'. July 2015. Submitted on behalf of ITD Ltd.

References

EFSA (European Food Safety Authority), 2008. Guidelines for the submission of an application for safety evaluation by the EFSA of a recycling process to produce recycled plastics intended to be used for manufacture of materials and articles in contact with food, prior to its authorisation. The EFSA Journal 2008, 717, 2–12.

EFSA Panel on Food Contact Materials, Enzymes, Flavourings and Processing Aids (CEF), 2011. Scientific Opinion on the criteria to be used for safety evaluation of a mechanical recycling process to produce recycled PET intended to be used for manufacture of materials and articles in contact with food. EFSA Journal 2011;9(7):2184, 25 pp. doi:10.2903/j.efsa.2011.2184


Appendix A – Technical data of the washed flakes as provided by the applicant of process Sumilon Eco PET SARL

Parameter	Value
Moisture maximum	1.0%
Bulk density	> 280 kg m ⁻³
Material temperature	10–60°C
Material temperature variation	± 10°C h ⁻¹
PVC maximum	50 ppm
Glue maximum	20-30 ppm
Polyolefins maximum	20 ppm
Metals maximum	20 ppm

Appendix B – Technical data of the washed flakes as provided by the applicant of process ITD

Parameter	Value
Moisture maximum	1.0%
Bulk density	> 280 kg m ⁻³
Material temperature	10–60°C
Material temperature variation	± 10°C h ⁻¹
PVC maximum	50 ppm
Glue maximum	500 ppm (inclusive flakes)
Polyolefins maximum	20 ppm
Metals maximum	20 ppm

Appendix C – Relationship between the key parameters for the evaluation scheme (EFSA CEF Panel, 2011)

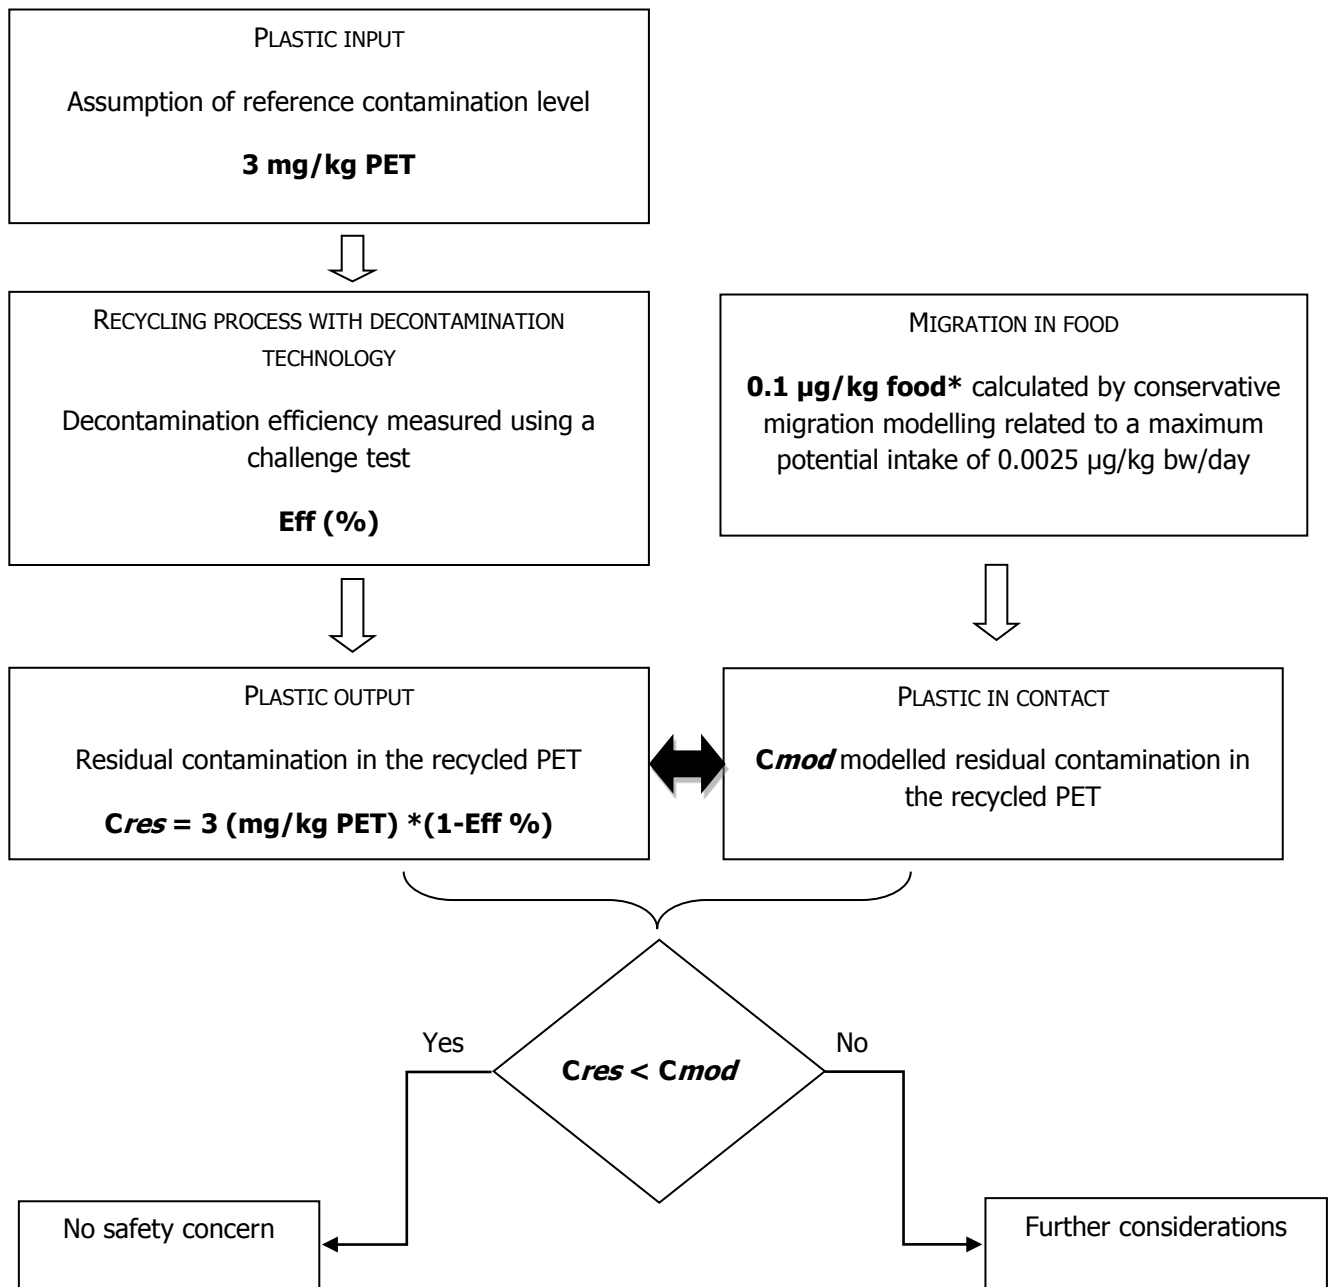

*Default scenario (infant). For adults and toddlers, the migration criterion will be 0.75 and 0.15 µg/kg food, respectively.

Abbreviations

bw	body weight
CEF	Food Contact Materials, Enzymes, Flavourings and Processing Aids
<i>C_{mod}</i>	modelled concentration in PET
<i>C_{res}</i>	residual concentrations in PET
EC	European Commission
EU	European Union
PET	poly(ethylene terephthalate)
ppm	parts per million
PVC	poly(vinyl chloride)
SSP	solid state polycondensation